

Chemical Resistance And Impact Properties Of Bamboo / Glass Fibers Reinforced Polyester Hybrid Composites

H. Raghavendra Rao¹, P. Hari Sankar¹ and M. Murali Mohan¹

Department of Mechanical Engineering, G.P.R. Engineering College, Kurnool – 518005, India

Corresponding Email: hanchatterao@gmail.com

Abstract— The chemical resistance of Bamboo/Glass reinforced epoxy hybrid composites to acetic acid, Nitric acid, Hydrochloric acid, Sodium hydroxide, Sodium carbonate, Benzene, Toluene, Carbon tetrachloride and Water was studied. The impact properties of these composites were also studied. The effect of alkali treatment of bamboo fibers on these properties was studied. It was observed that the impact properties of the hybrid composites increase with glass fiber content. These properties found to be higher when alkali treated bamboo fibers were used in hybrid composites. The hybrid fiber composites showed better resistance to the chemicals mentioned above. The elimination of amorphous hemi-cellulose with alkali treatment leading to higher crystallinity of the bamboo fibers with alkali treatment may be responsible for these observations.

.Keywords— Bamboo Fiber, Composites, Chemical Resistance, Polyester, Impact Strength, Glass Fiber

I. Introduction

Several studies on the composites made from polyester matrix and natural fibers like Jute, Wood, Banana, Sisal, Cotton, Coir and Wheat Straw were reported in the literature. Jindal, (1986) reported the development of bamboo fiber reinforced plastic composites using araldite (CIBA CY 230) resin as matrix. Though bamboo is extensively used as a valuable material from times immemorial (because of its high strength and low weight) the studies on this fiber reinforced plastics are meager. In the present work, the bamboo/glass fiber reinforced high performance polyester composites were developed and their impact properties with fiber content (with varying ratio of glass/bamboo fibers) were studied. The effect of alkali treatment of the bamboo fibers on these properties was also studied. The chemical resistance properties with varying fiber percentage were also studied.

II. Materials and Methods

Materials

High performance polyester resin were used as the matrix. Bamboo fibers (*Dendrocalamus Strictus*) were procured from

Tripura State of India in the dried form. Some of these fibers were soaked in 1% of NaOH solution for 30 min. to remove any greasy material and hemi cellulose. Washed thoroughly in distilled water and dried under the sun for one week. The fibers with a thickness of 0.3 mm were selected in the mat form. The Glass fibers (chopped form) have been procured from company (Owens Corning Fiber Glass Mat, Bombay) is used in making the hybrid composite percentage.

Preparation of Mould

For making the composites, a moulding box was prepared with glass with 200mm×200mm×3mm mould (length × width × thickness).

Preparation of the composite and the test specimens

The mould cavity was coated with a thin layer of aqueous solution of *Poly Vinyl Alcohol* (PVA) which acts as a good releasing agent. Further a thin coating of hard wax laid over it and finally another thin layer of PVA was coated. Each coat was allowed to dry for 20 minutes at room temperature.

A 3mm thick plate was made from the epoxy and hardener taken in the ratio of 100 and 10 parts by weight respectively. Then the moulding box was loaded with the matrix mixture, bamboo and glass fiber in random orientation (with varying percentage) and was placed in vacuum oven which was maintained at 100°C for 3 hours to complete the curing. After curing, the plate was removed from the moulding box with simple tapering and it was cut into samples for Impact test 120mm × 13mm × 3mm and for chemical test with dimensions of 10mm × 5mm × 5mm. For comparison sake the specimen for matrix were also prepared in similar lines.

III. Experimental Details

The impact strength is determined using IZOD impact tester. The test specimens with dimensions 120mm × 13mm × 3 mm are cut as per ASTM D 256-88 specifications. In each case five specimens are tested and average value is recorded.

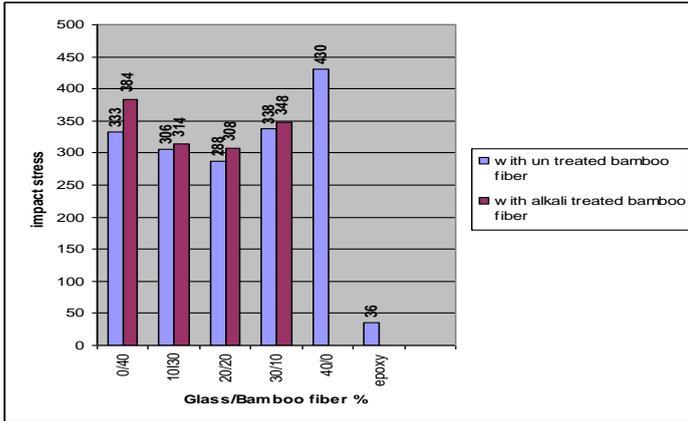


Figure.1 The variation of impact strength with the ratio of % Glass/Bamboo fibers reinforced epoxy composites.

CHEMICAL RESISTANCE OF COMPOSITES:

The chemical resistance of the composites was studied as per ASTM D 543-87 method. For chemical resistance test, the acids namely concentrated hydrochloric acid (10%), concentrated nitric acid (40%) and glacial acetic acid (8%), the alkalis namely aqueous solutions of sodium hydroxide (10%), ammonium hydroxide (10%) and sodium carbonate (20%) and the solvents- Benzene, Carbon tetra chloride, Toluene and Water were selected. In each case, ten pre-weighted samples were dipped in the respective chemicals under study for 24 hours, removed and immediately washed thoroughly with distilled water and dried by pressing them on both sides by filter papers. The final weight of the samples and % weight loss/gain was determined. The resistance test was repeated for ten samples in each case and the average values are reported.

Chemicals	Matrix	Composite
40% nitric acid	+0.2169	+0.25491
10% Hydrochloric acid	+0.9665	+0.25491
8% Acetic acid	+0.3965	+2.4299
10% sodium hydroxide	-0.4361	-2.7191
20% sodium carbonate	+0.777	-3.9756
10% Ammonium Hydroxide	-0.3973	-2.9185
Benzene	-1.371	-1.346
Toluene	-0.691	-2.360
Carbon tetrachloride	-1.134	+4.4458
Water	-1.212	-1.626

IV. RESULTS AND DISCUSSION

The variation of impact stress with percentage glass/bamboo fiber ratio is presented in (Fig 1). For comparison, these values for the matrix are also presented in the same figure. From the figure it is evident that the impact properties are enhanced when the alkali treated bamboo fibers were used in the hybrid composites. This is understandable as the hemi cellulose and the lignin contents decrease leading to higher percentage of crystalline α -cellulose in bamboo fibers on alkali treatment. The minimum and maximum values of impact strength for these composites are found to be 288 and 430 MPa respectively. Similar observation was made by Varadarajulu *et al.* (1998 – 2004) and Srinivasulu *et al.* (2006) in the case of some fiber composites and polymer coated bamboo fibers.

The effect of some acids, alkalis and solvents on the matrix and composite under study is presented in Table-1. From this table it is clearly evident that for matrix and composite, the weight gained is observed after immersion. This is understandable as the matrix is cross linked and as a result formation of gel takes place instead of dissolution. Similar observation was made by Varadarajulu *et al.* (1998 – 2004) in the case of short bamboo fiber reinforced high performance epoxy composites. It is also observed that the effect of sodium carbonate, benzene, toluene and carbon tetra chloride is negligible on both the matrix and composites. The chemical resistance of the hybrid composites with treated bamboo fibers is found to be better for the chemicals mentioned.

V. Conclusions

The hybrid composites of bamboo/glass fiber reinforced epoxy were made and their impact and chemical resistance properties were studied. The effect of alkali treatment of the bamboo fibers on these properties was studied. These hybrid composites were found to exhibit good impact and chemical resistance properties. The hybrid composites with alkali treated bamboo fibers were found to possess higher impact properties. The composites were found to be resistant to some acids, alkalis and solvents. The elimination of amorphous weak hemi cellulose components from the bamboo fibers on alkali treatment may be responsible for this behavior.

REFERENCES

- i. Jindal, U.C *development and testing of bamboo fibers reinforced plastic composites journal of composites.* 20: 19 (1986)
- ii. Varada Rajulu , A., Narasimha Chary, K., Rama Chandra Reddy, G. *Void content, density, weight reduction and mechanical properties of short bamboo fibers/ styrenated polyster composites. j. Bamboo & Rattan.* 2(2):95-102(2003).
- iii. Varada Rajulu, A., Narasimha Chary, K., Rama Chandra Reddy, G., Meng, Y.Z. *Void content, density, weight reduction and mechanical*

- properties of short bamboo fibers/ styrenated polyester composites. j. reinforced plastics and composites. 23(2):127-130.(2004).*
- iv. Varada Rajulu, A., Babu Rao, G ., Lakshminarayana Reddy, R. *Chemical resistance and tensile properties of epoxy/poly carbonate blend coated bamboo fibers, journal of reinforced plastics and composites. 20(4):335-340.(2001).*
 - v. Varada Rajulu, A., Ganga Devi, L., Babu Rao, G., Lakshminarayana Reddy, R. *Chemical resistance and tensile properties of epoxy/unsaturated blend coated bamboo fibers, journal of reinforced plastics and composites. 22(11) : 1029-1034. (2003).*
 - vi. Varada Rajulu, A., Allah Baksh, S., Narasimha Chary Reddy, G., *Chemical resistance and tensile properties of short bamboo fiber reinforced epoxy composites, journal of reinforced plastics and composites. 17(17): 1507-1511(1998).*
 - vii. Varada Rajulu, A., Narasimha Chary, K., Rama Chandra Reddy, G., Babu Rao, G.,Ganga Devi, L *Thermo gravimetric analysis of dendro calamus strictus bamboo fibers, journal of bamboo and Rattan. 1(3): 247-250.(2002).*
 - viii. Varada Rajulu, A., Narasimha Chary, K., Rama Chandra Reddy, G., *Chemical resistance and tensile properties of styrenated polyester – coated bamboo fibers, journal of fiber and textile research.. 23: 49-51(1998).*
 - ix. Varada Rajulu, A., Narasimha Chary, K., Rama Chandra Reddy, G. *Chemical resistance and tensile properties of epoxy - coated bamboo fibers, Indian journal of fiber and textile research. 21: 223-224. (1998).*
 - x. Srinivasulu, S., Varada Rajulu, A ., Narasimha Chary, K., Rama Chandra Reddy, G. *Chemical resistance and tensile properties of poly carbonate toughened epoxy - bamboo fibers, bulletin of pure and applied sciences. 25(2):137-142. (2006).*